

## HEAT FLOW KINETICS IN THE MOULDING SAND

CHOLEWA Mirosław, KOZAKIEWICZ Łukasz

*Faculty of Mechanical Engineering, Department of Foundry, Silesian University of Technology, Gliwice, Poland, EU, [lukasz.kozakiewicz@polsl.pl](mailto:lukasz.kozakiewicz@polsl.pl)*

### Abstract

Attempt to determine the heat flow kinetics in insulating moulding sand with aluminosilicate microspheres matrix in order to identify and modify its properties. Destination of moulding sand is pouring thin-walled skeletal casting 3D, characterized by strongly developed surface of heat dissipation and 1.5 ÷ 3 mm predicted connector thickness. It will be shown the results of computer simulation of temperature field in the mould. For the implementation of the research it was used the eutectic aluminum alloy with silicon (AlSi12). The results of the heat flow in the cast-mould system using experimental casting typically for thermal derivative gradient analysis (TDGA) are shown. The method was developed in the Department of Foundry of Silesian University of Technology. For the purpose of the own research the methodology has been modified by location most of the thermocouple not in the cast, but in the moulding sand. Thermocouples were placed in established and variable distances in the range of 0 to 8 mm from the surface of the casting. One of the thermocouple was placed in the geometric centre of the casting. Simulation study was performed, which aim was precision analysis of heat flow in the mould. This analysis is the basis for the designation of thermophysical and technological parameters of mould or core sand. The aim is to estimate the thermophysical of technology quantity in actual industrial environments. Application of the concept of TDGA methods in the assumption should allow obtain quickly the information about thermal properties of mould without uses of complex thermal laboratory research. It was assumed that the analysis of the temperature field gives the qualitatively comparable results to the standard determining of thermal properties in a function of temperature. Despite the simplifications, the importance of technological methods may prove to be attractive in the production conditions of a typical foundry.

**Keywords:** Aluminosilicate microspheres, moulding sand, heat flow, TDGA

### 1. INTRODUCTION

Control of crystallization parameters, in particular the rate of heat removal, has a fundamental role in the production of castings. Proper design of the mould is not easy. There is difficult and expensive process. An important tool for engineers, which significantly facilitates the process of developing technology, is a special computer software. It allows perform the simulations of complex thermal processes occurring during casting. Greatly shortens the implementation process technology, too [1].

### 2. SIMULATION PROGRAMS

Simulation programs, both in the foundry and broadly defined other branches of industry, have an important role. On the one hand they allow fine-tune manufacturing processes without the need for laborious technical tests, on the other hand visualize a series of phenomena occurring during the process proceed. The examples of practical use of computer simulation in foundry can be found at:

- a) conduct metal place control and pouring system,
- b) evaluation of the functioning of risers, optimize their size, shape and location of the casting,
- c) check the connections methods of risers with cast and insulation materials activities,
- d) search for alternative ways of eliminating porosity, e.g. through the use of external chill or cooling fins,


- e) depict the crystallization process and the designation of time after which the cast reaches the right temperature for knocking out,
- f) determining the stress field in casting and sites vulnerable to breakage,
- g) casting structure prediction and appearance e.g. hard spots in cast iron etc.,
- h) estimating the kinetics of phase transformations that occur in the solid cast during its cooling down and during the various thermal treatment.

Simulations of all these phenomena can be successfully used in the analysis of the tests described in literature [2-9]. Simulation processes and results of research related to heat flow, predicting the microstructure or description of the process in foundry are described in the papers [10-14].

### 3. RANGE OF STUDIES

The aim of the study is presenting and analyzing the results of computer simulation of heat flow in a cast-mould system using experimental casting typically for thermal derivative gradient analysis (TDGA) [15]. Experimental casting has a cone shape.

In the framework of the research casting model and mould were made in the SOLID EDGE programme. In programme NOVAFLOW&SOLID desirable materials both parts were assigned, then 6 sensors in the mould at different position of high were located (similarly in the TDGA method). Sensors were placed on the rising spiral of the curve. 1 sensor was placed in the geometric centre of the casting. Thermocouples were located at the mould-casting contact and in the mould in 2, 4, 6 or 8 mm distance from the casting. Localization of thermocouple is shown in **Fig. 1**. In subsequent simulations sensors distance from casting surface were edited.

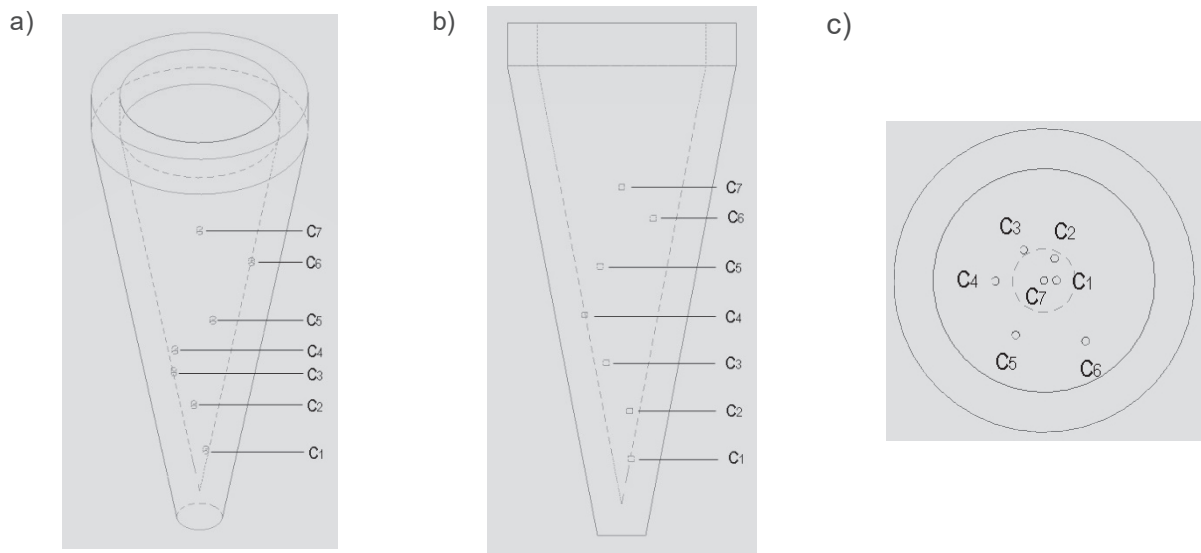

**Fig. 1** Examples of arrangement of sensors C1 ÷ C6 in the mould enclosing cone experimental casting. C7 sensor is located in the geometric centre of the experimental casting

### 4. RESULTS OF STUDIES

The results of the maximum temperature values and the corresponding times are shown in **Tables 1, 3, 5, 7, 9**. Temperature measurement at intervals of 100 seconds is shown in the **Tables 2, 4, 6, 8, 10**. **Figs. 2 to 6** present the cooling curves obtained by simulation. Pouring temperature is assumed to be equal to the 680 °C.


**4.1. Sensors placed at the mould-casting contact**

**Table 1** Maximum temperature and the duration of its occurrence reported at the mould-casting contact

Sensor No.	C1	C2	C3	C4	C5	C6	C7
Max. temp. [°C]	653	680	595	608	648	678	681
Time [s]	1	1	8	8	6	4	3

**Table 2** Temperature measurement [°C] at intervals of 100 seconds at the mould-casting contact

Time [s]	C1	C2	C3	C4	C5	C6	C7
100	552	572	556	556	548	573	574
200	387	390	381	371	363	377	379
300	240	246	241	234	226	230	234
400	156	163	161	157	152	154	156
500	106	113	113	111	109	112	111
600	84	91	91	91	90	93	91

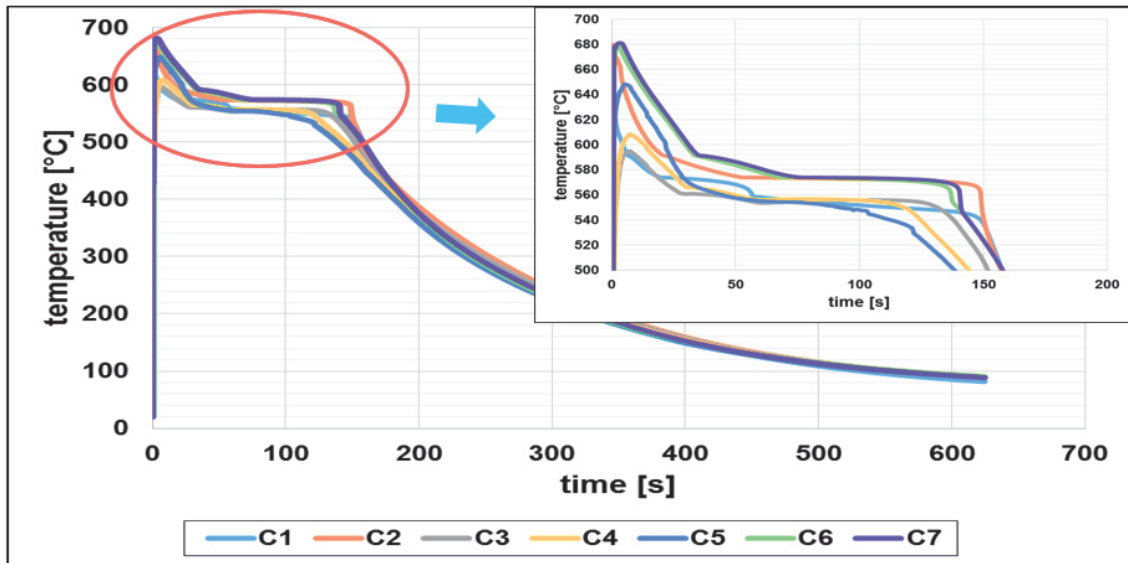

**Fig. 2** Temperature change at the mould-casting contact

**4.2. Sensors placed in 2 mm from casting surface distance**

**Table 3** Maximum temperature and the duration of its occurrence reported in 2 mm from casting surface distance

Sensor No.	C8	C9	C10	C11	C12	C13	C14
Max. temp. [°C]	435	446	391	439	405	499	681
Time [s]	142	143	136	120	104	127	3

**Table 4** Temperature measurement [°C] at intervals of 100 seconds in 2 mm from casting surface distance

Time [s]	C8	C9	C10	C11	C12	C13	C14
100	428	434	375	433	405	496	574
200	329	345	320	339	296	362	379
300	206	223	214	220	192	221	234
400	137	150	148	150	130	148	156
500	93	102	103	105	93	105	111
600	74	81	82	85	78	86	91

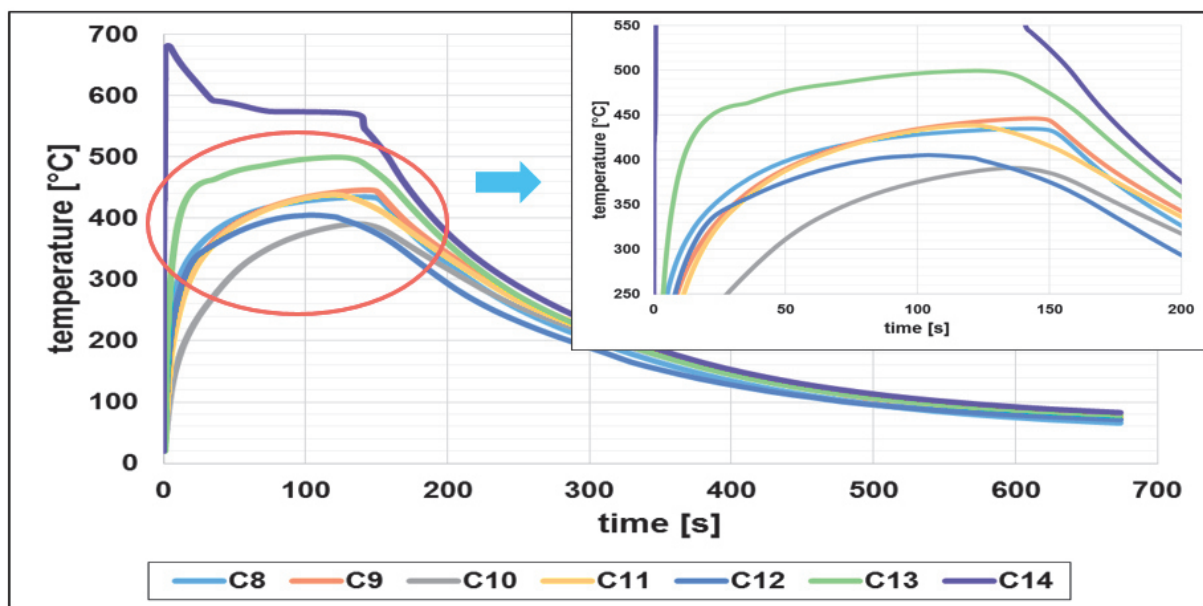


Fig. 3 Temperature change in 2 mm from casting surface distance

The highest maximum temperature in the mould recorded thermocouple C13 located at the altitude of 102 mm, indicated temperature nearly 500 °C. The lowest maximum temperature should be noted by sensor, which is the lowest because of the smallest volume of liquid metal in the place of its location. That is connected with the fastest heat loss from the beginning of the pouring process. The lowest temperature (391 °C) was pointed by sensor C10 positioned at height of 51 mm. It can be the result of a small mesh concentration, which preclude accurately arrangement of the sensors. As the consequences the thermocouple C10 could be placed far away from the outside surface of casting than the other thermocouple.

#### 4.3. Sensors placed in 4 mm from casting surface distance

**Table 5** Maximum temperature and the duration of its occurrence reported in 4 mm from casting surface distance

Sensor No.	C15	C16	C17	C18	C19	C20	C21
Max temp. [°C]	308	322	323	343	310	380	681
Time [s]	152	152	145	133	127	139	3

**Table 6** Temperature measurement [°C] at intervals of 100 seconds in 4 mm from casting surface distance

Time [s]	C15	C16	C17	C18	C19	C20	C21
100	288	296	300	327	303	363	574
200	261	279	280	291	261	317	377
300	174	189	192	193	174	193	222
400	119	131	133	133	121	131	148
500	86	95	98	99	92	97	111
600	68	75	78	80	76	80	91

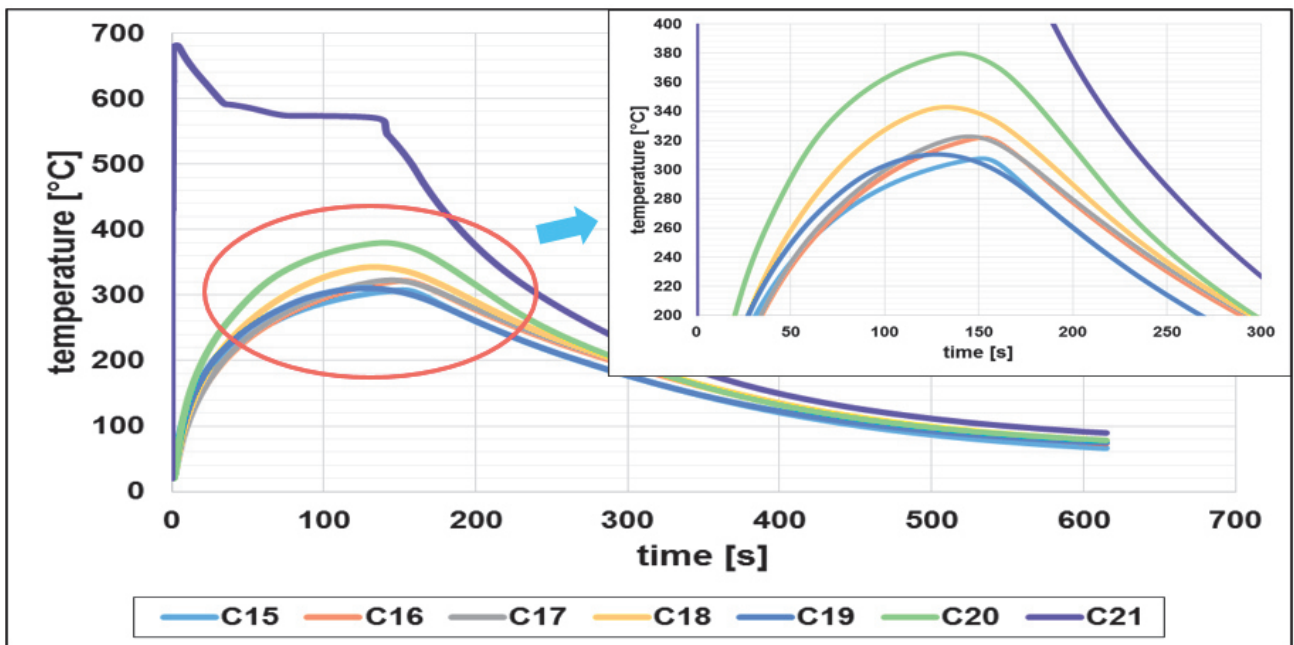


Fig. 4 Temperature change in 4 mm from casting surface distance

It can be noted a significant decrease of the maximum value of temperature relative to the sensors placed 2 mm from the casting. The highest temperature in 4 mm distance from the inner surface of the mould indicate the sensor embedded the highest, i.e. C20 with a score of 380 °C. The second highest maximum temperature of thermocouple indicated C18 located at an altitude of 68 mm. It may be the result of thermal centre of cast effect. At the same height the tendency to create the shrinkage has been observed.


#### 4.4. Sensors placed in 6 mm from casting surface distance

Table 7 Maximum temperature and the duration of its occurrence reported in 6 mm from casting surface distance

Sensor no	C22	C23	C24	C25	C26	C27	C28
Max temp. [°C]	255	285	269	291	255	296	681
Time [s]	157	155	153	143	141	152	3

**Table 8** Temperature measurement [°C] at intervals of 100 seconds in 6 mm from casting surface distance

Time [s]	C22	C23	C24	C25	C26	C27	C28
100	237	261	249	273	245	273	574
200	233	258	249	262	234	270	379
300	167	186	184	187	168	184	234
400	117	132	132	133	120	128	155
500	81	91	93	94	87	91	110
600	64	73	74	76	72	75	91

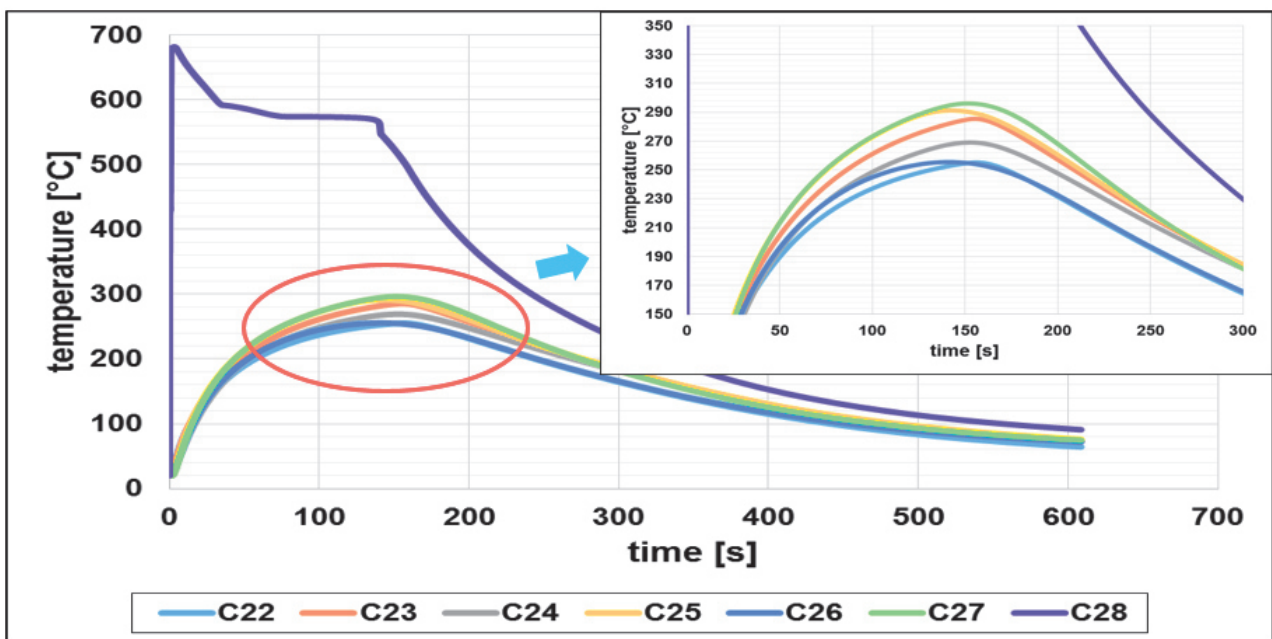

**Fig. 5** Temperature change in 6 mm from casting surface distance

As in previous simulations, the highest temperature at the highest arranged sensor were observed. The order of the individual measurement of the maximum temperatures is the same as for simulation No. 3. Recorded the highest results consistently fall down in relation to measurements the sensors located closer to the outer surface of casting.


**4.5. Sensors placed in 8 mm from casting surface distance**

**Table 9** Maximum temperature and the duration of its occurrence reported in 8 mm from casting surface distance

Sensor No.	C29	C30	C31	C32	C33	C34	C35
Max temp. [°C]	210	225	216	239	216	268	681
Time [s]	163	164	164	152	150	156	3

**Table 10** Temperature measurement [°C] at intervals of 100 seconds in 8 mm from casting surface distance

Time [s]	C29	C30	C31	C32	C33	C34	C35
100	194	206	200	224	206	248	574
200	200	215	208	225	205	251	379
300	150	164	160	168	153	177	234
400	108	120	118	122	111	124	155
500	76	84	85	87	81	88	110
600	60	67	68	71	67	73	91

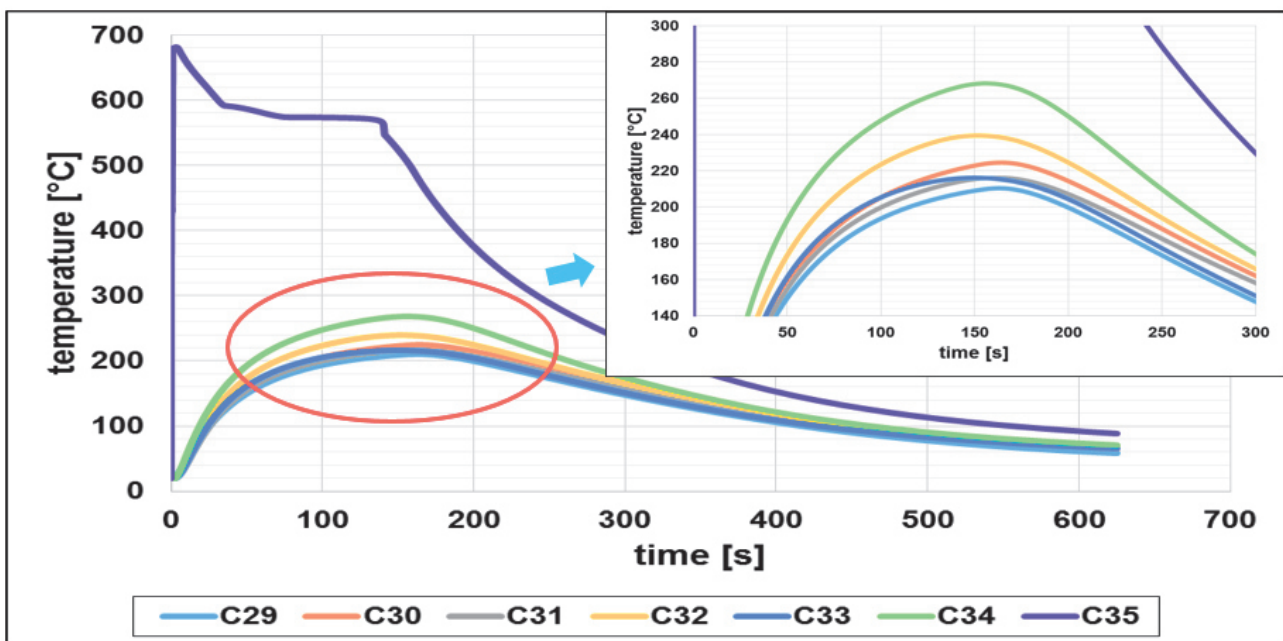

**Fig. 6** Temperature change in 8 mm from casting surface distance

Observed that the drop of temperature in 8 mm distance from the outer surface of casting in comparison to previous simulation is much smaller. The difference between the highest maximum temperature and the lowest is less than 70 °C. In the simulation, where thermocouple were placed just 2 mm from the outer surface of casting, difference amounted more than 108 °C.

## 5. CONCLUSIONS

Based on conducted studies following conclusions have been formulated:

- 1) due to the possibility of accommodate of measurement sensor, simulation program allows check the temperature distribution during the pouring and self-cooling process any place of moulds and cast;
- 2) the simulations gave the chance to check how intensively is heat removal from casting to mould,
- 3) presented concept allows estimate the thermal properties of the moulding sand for casting with varying thickness,
- 4) simulations results require practical experimental verification.

**REFERENCES**

- [1] KLUSKA-NAWARECKA S., POŁCIK H. Modelling problems and crystallization process control of aluminum alloys and copper alloys. *Foundry Archive*, Vol. 4, No. 14, 2004, pp. 215-220.
- [2] WRÓBEL T. Characterization of bimetallic castings with an austenitic working surface layer and an unalloyed cast steel base. *Journal of Materials Engineering and Performance*, Vol. 23, No. 5, 2014, pp. 1711-1717.
- [3] STAWARZ M. Influence of technological parameters on the microstructure of the silicon cast iron. In *METAL 2013. 22<sup>nd</sup> International Conference on Metallurgy and Materials*. Brno: TANGER, 2013, pp. 92-96.
- [4] STAWARZ M., JANERKA K., JEZIERSKI J., SZAJNAR J. Thermal effect of phase transformations in high silicon cast iron. In *METAL 2014. 23<sup>rd</sup> International Conference on Metallurgy and Materials*. Brno: TANGER, 2014, pp. 123-128.
- [5] JEZIERSKI J., JANERKA K., STAWARZ M. Theoretical and practical aspects of pneumatic powder injection into liquid alloys with non-submerged lance. *Archives of Metallurgy and Materials*, Vol. 59, No. 2, 2014, pp. 731-734.
- [6] JEZIERSKI J., JANERKA K. Parameters of a gas-solids jet in pneumatic powder injection into liquid alloys with a non-submerged lance. *Metalurgija*, Vol. 54, No. 2, 2015, pp. 365-367.
- [7] CHOLEWA M., KOZAKIEWICZ Ł. Strength properties of moulding sand for thin-walled casting production. In *METAL 2014. 23<sup>rd</sup> International Conference on Metallurgy and Materials*. Brno: TANGER, 2014, pp. 1294-1300.
- [8] CHOLEWA M., KOZAKIEWICZ Ł. Heat flow in the cast-mould system for moulding with gypsum and cement binder. *Archives of Foundry Engineering*, Vol. 15, No. 2, 2015, pp. 5-8.
- [9] SZAJNAR J., DULSKA A., WRÓBEL T., SUCHOŃ J. Diffusion of C and Cr during creation of surface layer on cast steel casting. *Archives of Metallurgy and Materials*, Vol. 59, No. 3, 2014, pp. 1085-1087.
- [10] VIJAYARAM T.R., SULAIMAN S., HAMOUDA A.M.S., AHMAD M.H.M. Numerical simulation of casting solidification in permanent metallic molds. *Journal of Materials Processing Technology*, Vol. 178, 2006, pp. 29-33.
- [11] GEORGIEV G.E., POPOV S., MANOLOV V., DIMITROVA R., KUZMANOV P. Heat transfer process computer simulation and microstructure prediction during crystallization of metal alloys. *Journal of Theoretical and Applied Mechanics*, Vol. 43, No. 1, 2013, pp. 71-78.
- [12] ANJO V. Numerical simulation of steady state conduction heat transfer during the solidification of aluminum casting in green sand mould. *Leonardo Electronic Journal of Practices and Technologies*, Vol. 20, 2012, p. 15-24.
- [13] PARIONA M.M., MOSSI A.C. Numerical simulation of heat transfer during the solidification of pure iron in sand and mullite molds. *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, Vol. 27, No. 4, 2005, pp. 399-406.
- [14] KONOPKA Z., ŁĄGIEWSKA M., ZYSKA A. Evaluation of the heat transfer coefficient at the metal-mould interface during flow. *Archives of Foundry Engineering*, Vol. 20, No. 4, 2007, pp. 101-104.
- [15] CHOLEWA M., JURA Z., STUDNICKI A. Development of thermal analysis and derivative methods at the Department of Foundry of Silesian University of Technology. *Archives of Foundry Engineering, Monography*, 2009, pp. 49-70.